

Synthesis of block copolymers by mechanistic transformation from reversible complexation mediated living radical polymerization to the photoinduced radical oxidation/addition/deactivation process

Aydogan, Canus; Aykac, F. Simal; Yilmaz, Gorkem; Chew, Ye Qiu; Goto, Atsushi; Yagci, Yusuf

2022

Aydogan, C., Aykac, F. S., Yilmaz, G., Chew, Y. Q., Goto, A. & Yagci, Y. (2022). Synthesis of block copolymers by mechanistic transformation from reversible complexation mediated living radical polymerization to the photoinduced radical oxidation/addition/deactivation process. *ACS Macro Letters*, 11(3), 342-346.

<https://dx.doi.org/10.1021/acsmacrolett.2c00004>

<https://hdl.handle.net/10356/156747>

<https://doi.org/10.1021/acsmacrolett.2c00004>

This document is the Accepted Manuscript version of a Published Work that appeared in final form in *ACS Macro Letters*, copyright © American Chemical Society after peer review and technical editing by the publisher. To access the final edited and published work see <https://doi.org/10.1021/acsmacrolett.2c00004>.

Synthesis of Block Copolymers by Mechanistic Transformation from Reversible Complexation Mediated Living Radical Polymerization to Photoinduced Radical Oxidation/Addition/ Deactivation Process

Cansu Aydogan¹, F.Simal Aykac¹, Gorkem Yilmaz¹, Ye Qiu Chew², Atsushi Goto^{2*}, Yusuf Yagci^{1,3*}

¹*Department of Chemistry, Faculty of Science and Letters, Istanbul Technical University, 34469 Maslak, Istanbul, Turkey*

²*Division of Chemistry and Biological Chemistry, School of Physical and Mathematical Sciences, Nanyang Technological University, 21 Nanyang Link, 637371, Singapore*

³*Faculty of Science, Chemistry Department, King Abdulaziz University, 21589 Jeddah, Saudi Arabia*

KEYWORDS Light induced polymerizations, Block copolymers, Mechanistic transformation.

ABSTRACT: A versatile strategy for the fabrication of block copolymers by the combination of two discrete living polymerization techniques; reversible complexation mediated living radical polymerization (RCMP) and photoinduced radical oxidation addition deactivation (PROAD) processes is reported. Firstly, RCMP is conducted to yield poly(methyl methacrylate) with iodide end groups (PMMA-I). In the following step, PMMA-I is used as macroinitiator for living PROAD cationic polymerization of isobutyl vinyl ether. Successful formation of the block copolymers is confirmed by ¹H NMR, FT-IR, GPC, and DSC investigations.


Recently, block copolymers have been the subject of detailed investigations as they are excellent candidates for various applications such as adhesives, drug delivery, nanomedicine, soft lithography and thermoplastic elastomers due their range of desirable properties emerging from each discrete monomer segments.¹⁻⁷ The possibility of adjusting structural and compositional versatility of each segments to tune the physicochemical properties on demand, have pushed the research frontiers toward the development of novel synthetic strategies for the preparation of block copolymers.⁸⁻¹¹ Traditionally, anionic living polymerization (LP) was employed for the synthesis of block copolymers using sequential monomer addition technique. However, the current research progress is closely related to contemporary radical polymerization methods as well as cationic polymerization as they require easy experimentation procedures.¹²⁻¹⁹

In recent years, mechanistic transformation techniques has been widely employed for expanding the scope of variations of block or graft copolymers by the combination of different polymerization modes. Mechanistic transformations were successfully applied to all types of addition polymerizations; radical, cationic, and anionic polymerizations.^{28,29} Using this approach, block copolymers that can

not be obtained by a single polymerization mode, can be prepared efficiently. Mechanistic transformations can be realized by two distinct strategies, namely direct and indirect transformation reactions. Direct transformation refers the transformation of a propagating active center to another active center with different polarity. In general, such transformation occurs through electron transfer process. Indirect transformation technique considers introduction of the stable but potentially reactive functional group for the second polymerization mode at the chain ends, either in the initiation or in the termination steps of the polymerization of the first monomer. After the isolation and purification of the polymer, finally the functional groups are converted to another species.³⁰ Intriguing developments on controlled/living polymerizations by radical and cationic mechanisms with the capability to control over functional groups and molecular weight opened new routes for mechanistic transformations.³¹⁻³⁹

Controlled/living radical polymerization (CLRP) also called reversible deactivation radical polymerization (RDRP), has widely been used as an efficient tool for the synthesis of well-defined polymers with low dispersity. The mechanism is grounded on the reversible activation of the dormant species (Polymer-X) to the propagating radical

(Polymer•) using certain additives. The most common LRP techniques are atom transfer radical polymerization^{40,41} (ATRP), reversible addition-fragmentation-transfer polymerization^{42,43} and nitroxide mediated polymerization.⁴⁴ Goto and co-workers presented a novel method coined “reversible complexation mediated polymerization” (RCMP) for the synthesis of polymers with well-defined structures.⁴⁵⁻⁴⁸ It considers the use of alkyl iodides as initiator and organic salts such as tetrabutylammonium iodide as catalyst, which provides reversibly generation of R•. The catalyst activates Polymer-I to form Polymer• and A⁺I₂⁻ (Scheme 1). After incorporation of a few monomers, Polymer• is deactivated by the radicalic salt catalyst to generate Polymer-I and A⁺I⁻ again. Polymer-I is also activated to Polymer• via degenerative chain transfer.⁴⁹ The contributions of the catalytic process and degenerative chain transfer depend on the systems.⁵⁰ By repeating activation–deactivation cycles, the polymer grows gradually resulting in the formation of polymers with low polydispersity (Scheme 1).




Scheme 1. General mechanism of RCMP.

Although cationic polymerization has been utilized for industrial applications for decades, bringing controlled/living features to cationic polymerization remained a challenge until Higashimura et al.⁵¹ and Kennedy et al.⁵² independently reported the living cationic polymerization of vinyl ethers and isobutylene, respectively.

Kamigaito *et al.* reported the living cationic polymerization of vinyl ethers, using acetic acid derivatives and Lewis acids as initiators.⁵³ The technique was improved by the use of zinc halides as additives to regulate the nucleophilicity of the chain ends, which overcome the necessity of using acids with nonnucleophilic counterparts such as PF₆⁻, SbF₆⁻ and BF₄⁻. Adaptation of this approach to a photochemical strategy has later been demonstrated by Yagci and co-workers for the preparation of poly(vinyl ether)s with controlled molecular weight characteristics.⁵⁴

Photoinduced radical oxidation addition deactivation (PROAD) processes has recently become an alternative way for the living cationic polymerization of vinyl ethers. The mechanism follows visible light induced halide abstraction followed by oxidation, addition and deactivation processes using alkyl halide, Mn₂(CO)₁₀ and diphenyliodonium bromide (Ph₂I⁺Br⁻) as the onium salt⁵⁵ (Scheme 2).

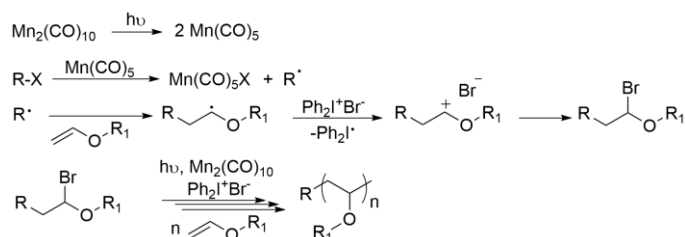


Scheme 2. Mechanism of PROAD polymerization of vinyl ethers.

Facilitated by the chain end fidelity, PROAD methodology was exploited for the realization of various mechanistic transformation reactions. For instance, block copolymers from cationically polymerizable vinyl ethers with vinyl monomers polymerizable by radical means, were prepared by combining iniferter with PROAD processes proceeding in a controlled manner.⁵⁶ In another study, two discrete living polymerization were united for the preparation of amphiphilic block copolymers. Bromo-end group of poly(methyl methacrylate) prepared by ATRP was converted to triphenylmethyl (trityl) functionality by visible light induced simultaneous halide abstraction and coupling reactions. The obtained polymers bearing trityl end groups acted as macroiniferter which enabled the polymerization of vinyl monomers to yield desired block copolymers in a controlled fashion. Poly(*tert*-butyl acrylate) based block copolymers are essentially converted to poly(acrylic acid) resulting in the formation of amphiphilic copolymers with a facile hydrolyzation protocol.⁵⁷ The current work was designed to combine RCMP with PROAD processes both proceeding in a controlled manner to produce block copolymers with well-defined structures by mechanistic transformation pathway. The presented approach is particularly useful as the type of the monomers used are structurally different and can not be combined by either mechanisms.

We first carried out RCMP of methyl methacrylate (MMA) (100 eq) using ethyl 2-iodo-2-phenylacetate (EPH-I) (1eq) and tetrabutylammonium iodide (BNI) (1.5 eq) at 60 °C for 2 h. In order to keep high iodide-chain end fidelity of the obtained polymer, we intentionally stopped the polymerization at a relatively short time (at a moderate monomer conversion of 31%). After purification via reprecipitation in hexane, we obtained a poly(methyl methacrylate)-iodide (PMMA-I) (*M_n* = 3900 and *M_w*/*M_n* = 1.12 after purification). A chain extension test of PMMA-I in an RCMP of MMA demonstrated a relatively high iodide-chain end fidelity (>86%) of PMMA-I (Supporting Information).

Poly (isobutyl vinyl ether) segments were photochemically attached to iodide chain-end polymers (PMMA-I) in the presence of Mn₂(CO)₁₀ in conjunction with an oxidant. In the process, PMMA-I served as macroinitiator and oxidized by Ph₂I⁺Br⁻ to give corresponding carbocation capable of inducing cationic living polymerization of isobutyl vinyl ether (IBVE) under visible light irradiation (Scheme 3).

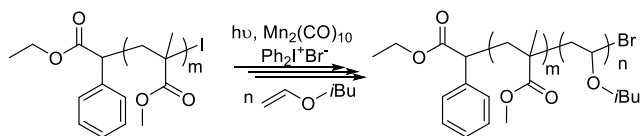

Scheme 3. Synthesis of block copolymers by the combination of RCMP and PROAD polymerizations

The block copolymerizations of IBVE with PMMA-I were performed under different experimental conditions, and the results are tabulated in Table 1.

Table 1. PROAD polymerization of IBVE using PMMA-I as precursor^a

Run	[Mn ₂ (CO) ₁₀]/ [Ph ₂ I ⁺ Br ⁻]	M _{n,NMR} (g/mol) ^b	M _{n,GPC} (g/mol) ^c	M _w /M _n ^c
1	0.25/0.25	12400	13900	1.57
2	0.25/0.5	11300	13000	1.56
3	0.5/0.25	11500	11700	1.70
4	0.1/0.25	13100	15000	1.61

^a M_n(PMMA-I): 3900 g/mol, [IBVE]/[PMMA-I]: 100/1, Propylene carbonate (PC) was used as solvent (V_{PC}/V_{IBVE}: 2/1) irradiation time = 90 min. ^b Determined by ¹H NMR: calculated by comparing the integral area of the sum of methine proton of PIBVE and methyl ester of PMMA with methylene proton of PIBVE. ^c Determined by gel permeation chromatography according to polystyrene standards.

The structure of the block copolymers was investigated by ¹H NMR and FT-IR spectral analyses. The signals between 3–3.5 ppm in the ¹H NMR spectrum (Figure 1) confirmed the successful attachment of IBVE segment to the precursor polymer. Similarly, FT-IR spectroscopy revealed the characteristic bands of the PMMA and the PIBVE segments. The sharp band at 1724 cm⁻¹ can be attributed to C=O stretching of PMMA while the etheric C-O-C stretching band observable at 1074 cm⁻¹ corresponds the incorporated PIBVE segment (Figure S1).

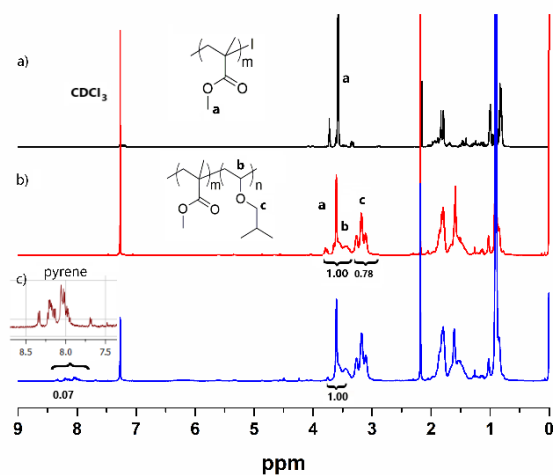


Figure 1. ¹H NMR spectra of a) PMMA, b) PMMA-*b*-PIBVE, c) pyrene functional PMMA-*b*-PIBVE.

Moreover, a clear shift to higher molecular weight region in GPC traces confirms successful block copolymerization process (Figure 2). Notably, no contamination of the precursor polymer was detected. The observed relatively broad dispersity can be attributed to slow addition of PMMA radical to vinyl ether as previously described.³⁸

Differential scanning calorimetry (DSC) investigation was further performed for the thermal characterization of the block copolymer. The glass transition peak of the pristine PMMA is detectable at 102 °C, while after block copolymerization, two glass transition temperatures were observed at -20 °C and 103 °C, corresponding to PIBVE and PMMA segments, respectively (Figure S2). This shows that the two segments are immiscible in this molecular weight composition.

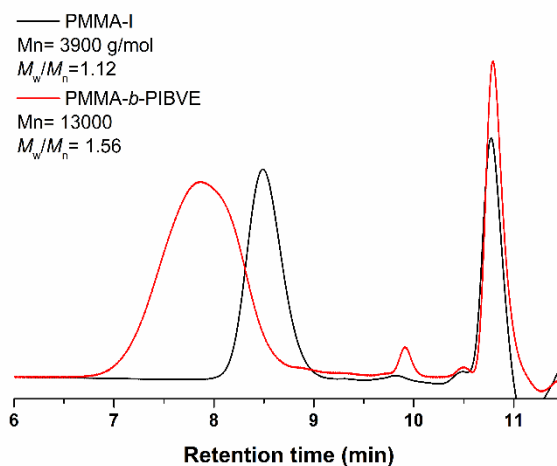


Figure 2. GPC traces of PMMA and PMMA-*b*-PIBVE.

The chain-end functionality of the block copolymers were not distinguishable probably due to the production of high molar mass polymers and/or the loss of the bromine functional group during the purification in methanol, which may lead to a substitution with methoxy groups.

To confirm the presence of bromide group at the chain end of polymers, the polymerization was terminated by adding pyrene-1-methanethiol to the reaction medium. This way, the chain-end of the block copolymer was modified with pyrene groups by a simple substitution reaction. Then, thus formed polymer was precipitated in methanol for purification. The incorporation of the pyrene moiety at the chain end was confirmed by NMR, UV and fluorescence analyses. The aromatic peaks observed around 7.7–8.3 ppm in the ¹H NMR spectrum of the block copolymer (Figure 1c), blue line) demonstrate the attachment of the aromatic rings. The strong absorption band above 300 nm in the UV spectrum (Figure S5a) and intense emission band above 400 nm in the fluorescence spectrum of the polymer (Figure S5b) clearly confirm the existence of the pyrene moieties at the chain ends of the polymer obtained. When the UV spectrum of the pyrene-attached block copolymer, PMMA-*b*-PIBVE-pyrene was compared with that of bare

pyrene at equal chromophore group concentrations, the absorption bands were found to be quite related (Figure S5a). Notably, polymer obtained without functionalization process has no absorption (Figure S5a, blue line). To further prove of the success of the chemical attachment of pyrene group at the chain end, and absence of any unreacted pyrene residue, molecular weight PMMA-*b*-PIBVE-pyrene, were calculated by NMR, GPC and UV analyses and compared. Using the molar extinction coefficient of bare pyrene in THF, which was found as $\epsilon = 30,000$ l/mol.cm, the molecular weight of the block copolymer was calculated as 11700, which is in agreement with $M_{n,NMR}$ and $M_{n,GPC}$, 13100 and 15000 g/mol, respectively (Run 4) The close values confirm successful functionalization and chain end fidelity of the block copolymer.

In conclusion, a novel transformation system for the fabrication of well defined block copolymers is proposed. This approach offers combination of two different living polymerization methods which allows to synthesize block copolymers with PMMA and PIBVE segments by sequential RCMP and PROAD processes, respectively. We believe that, this strategy widened the scope of mechanistic transformation reactions and may serve a platform for the development of new complex architectures.

ASSOCIATED CONTENT

SUPPORTING INFORMATION

Materials, synthesis of the polymers, additional spectral data.

AUTHOR INFORMATION

Corresponding Author

Atsushi Goto- Division of Chemistry and Biological Chemistry, School of Physical and Mathematical Sciences, Nanyang Technological University, 21 Nanyang Link, 637371, Singapore;; Email: agoto@ntu.edu.sg

Yusuf Yagci - Department of Chemistry, Faculty of Science and Letters, Istanbul Technical University, 34469 Maslak, Istanbul, Turkey; Faculty of Science, Chemistry Department, King Abdulaziz University, 21589 Jeddah, Saudi Arabia orcid.org/0000-0001-6244-6786; Email:yusuf@itu.edu.tr

Present Addresses

Cansu Aydogan- Department of Chemistry, Faculty of Science and Letters, Istanbul Technical University, 34469 Maslak, Istanbul, Turkey

F.Simal Aykac- Department of Chemistry, Faculty of Science and Letters, Istanbul Technical University, 34469 Maslak, Istanbul, Turkey

Gorkem Yilmaz- Department of Chemistry, Faculty of Science and Letters, Istanbul Technical University, 34469 Maslak, Istanbul, Turkey

Ye Qiu Chew- Division of Chemistry and Biological Chemistry, School of Physical and Mathematical Sciences, Nanyang Technological University, 21 Nanyang Link, 637371, Singapore

ACKNOWLEDGMENT

The authors would like to acknowledge the financial support from The Scientific and Technological Research Council of Turkey (Project Number: 120C121) and Istanbul Technical University Research Fund and National Research Foundation (NRF) Investigatorship in Singapore (NRF-NRF105-2019-0001).

REFERENCES

1. Discher, D. E.; Eisenberg, A., Polymer vesicles. *Science* **2002**, *297* (5583), 967-973.
2. Lodge, T. P., Block Copolymers: Past Successes and Future Challenges. *Macromol. Chem. Phys.* **2003**, *204* (2), 265-273.
3. Jeong, B.; Bae, Y. H.; Lee, D. S.; Kim, S. W., Biodegradable block copolymers as injectable drug-delivery systems. *Nature* **1997**, *388* (6645), 860-862.
4. Shin, J. J.; Kim, E. J.; Ku, K. H.; Lee, Y. J.; Hawker, C. J.; Kim, B. J., 100th Anniversary of Macromolecular Science Viewpoint: Block Copolymer Particles: Tuning Shape, Interfaces, and Morphology. *ACS Macro Lett.* **2020**, *9* (3), 306-317.
5. Cabral, H.; Miyata, K.; Osada, K.; Kataoka, K., Block Copolymer Micelles in Nanomedicine Applications. *Chem. Rev* **2018**, *118* (14), 6844-6892.
6. Yang, J.; Song, J.-I.; Song, Q.; Rho, J. Y.; Mansfield, E. D. H.; Hall, S. C. L.; Sambrook, M.; Huang, F.; Perrier, S., Hierarchical Self-Assembled Photo-Responsive Tubosomes from a Cyclic Peptide-Bridged Amphiphilic Block Copolymer. *Angew. Chem.* **2020**, *59* (23), 8860-8863.
7. Bates, C. M.; Maher, M. J.; Janes, D. W.; Ellison, C. J.; Willson, C. G., Block Copolymer Lithography. *Macromolecules* **2014**, *47* (1), 2-12.
8. Crivello, J. V., Radical-Promoted Visible Light Photoinitiated Cationic Polymerization of Epoxides. *J. Macromol. Sci., Part A.* **2009**, *46* (5), 474-483.
9. Hadjichristidis, N.; Pitsikalis, M.; Iatrou, H., Synthesis of Block Copolymers. In *Block Copolymers I*, Abetz, V., Ed. Springer Berlin Heidelberg: Berlin, Heidelberg, 2005; pp 1-124.
10. Serhatli, I. E.; Galli, G.; Yagci, Y.; Chiellini, E., Synthesis of hybrid liquid crystalline block copolymers by combination of cationic or promoted cationic and free-radical polymerizations. *Polym. Bull.* **1995**, *34* (5), 539-546.
11. Lessard, J. J.; Scheutz, G. M.; Sung, S. H.; Lantz, K. A.; Epps, T. H.; Sumerlin, B. S., Block Copolymer Vitrimers. *J. Am. Chem. Soc.* **2020**, *142* (1), 283-289.
12. Ciftci, M.; Norsic, S.; Boisson, C.; D'Agosto, F.; Yagci, Y., Synthesis of Block Copolymers Based on Polyethylene by Thermally Induced Controlled Radical Polymerization Using Mn₂(CO)₁₀. *Macromol. Chem. Phys.* **2015**, *216* (9), 958-963.
13. Kahveci, M. U.; Acik, G.; Yagci, Y., Synthesis of Block Copolymers by Combination of Atom Transfer Radical Polymerization and Visible Light-Induced Free Radical Promoted Cationic Polymerization. *Macromol. Rapid Commun.* **2012**, *33* (4), 309-313.
14. Aydogan, C.; Kutahya, C.; Allushi, A.; Yilmaz, G.; Yagci, Y., Block copolymer synthesis in one shot: concurrent metal-free ATRP and ROP processes under sunlight. *Polym. Chem.* **2017**, *8* (19), 2899-2903.
15. Yilmaz, G.; Yagci, Y.; Multi-mode Polymerizations Involving Photoinduced Radical Polymerization. *J. Photopolym. Sci. Technol.* **2018**, *31* (6), 719-725.
16. Acik, G.; Kahveci, M. U.; Yagci, Y., Synthesis of Block Copolymers by Combination of Atom Transfer Radical Polymerization and Visible Light Radical Photopolymerization Methods. *Macromolecules* **2010**, *43* (21), 9198-9201.

17. Kahveci, M. U.; Mangold, C.; Frey, H.; Yagci, Y., Graft Copolymers with Complex Polyether Structures: Poly(ethylene oxide)-graft-Poly(isobutyl vinyl ether) by Combination of Living Anionic and Photoinduced Cationic Graft Polymerization. *Macromol. Chem. Phys* **2014**, *215* (6), 566-571.
18. Yagci, Y.; Atilla Tasdelen, M., Mechanistic transformations involving living and controlled/living polymerization methods. *Prog. Polym. Sci.* **2006**, *31* (12), 1133-1170.
19. Hizal, G.; Yagci, Y.; Schnabel, W.; N-Alkoxy Pyridinium Ion Terminated Polytetrahydrofurans - Synthesis and Their Use in Photoinitiated Block Copolymerization. *Polymer* **1994**, *35* (20), 4443-4448.
20. Erdogan, T.; Bernaerts, K. V.; Van Renterghem, L. M.; Du Prez, F. E.; Goethals, E. J., Preparation of star block co-polymers by combination of cationic ring opening polymerization and atom transfer radical polymerization. *Des. Monomers Polym.* **2005**, *8* (6), 705-714.
21. Galli, G.; Chiellini, E.; Yagci, Y.; Serhatli, E. I.; Laus, M.; Bignozzi, M. C.; Angeloni, A. S., Block copolymers with crystalline and side-chain liquid crystalline blocks. *Die Makromol. Chemie, Rapid Comm.* **1993**, *14* (3), 185-193.
22. Mao, J.; Ji, X.; Bo, S., Synthesis and pH/Temperature-Responsive Behavior of PLLA-b-PDMAEMA Block Polyelectrolytes Prepared via ROP and ATRP. *Macromol. Chem. Phys.* **2011**, *212* (7), 744-752.
23. Yagci, Y.; Schnabel, W., Light-induced synthesis of block and graft copolymers *Prog. Polym. Sci* **1990**, *15*, 551.
24. Zhu, Y.; Storey, R. F., New Dual Initiators To Combine Quasiling Carbocationic Polymerization and Atom Transfer Radical Polymerization. *Macromolecules* **2010**, *43* (17), 7048-7055.
25. Yenice, Z.; Tasdelen, M. A.; Oral, A.; Guler, C.; Yagci, Y., Poly(styrene-b-tetrahydrofuran)/clay nanocomposites by mechanistic transformation. *J. Polym. Sci. Part A Polym. Chem.* **2009**, *47* (8), 2190-2197.
26. Yagci, Y., Block copolymers by combinations of cationic and radical routes. I: A new difunctional azo-oxocarbenium initiator for cationic polymerization. *Polym. Commun.* **1985**, *26* (1), 7-8.
27. Yagci, Y., Block copolymers by combinations of cationic and radical routes. II: Use of polymers with acyl chloride terminal groups in oxocarbenium polymerization. *Polym. Commun.* **1986**, *27* (1), 21-22.
28. Burgess, F. J.; Cunliffe, A. V.; MacCallum, J. R.; Richards, D. H. Reaction to effect the transformation of anionic polymerization into cationic polymerization: 1. Synthesis and reactivities of anionically generated bromine terminated polymers. *Polymer* **1977**, *18*(7) 719-725.
29. Aoshima, H.; Satoh, K.; Kamigaito, M. Direct Mechanistic Transformations from Isotactic or Syndiotactic Living Anionic Polymerizations of Methyl Methacrylate into Metal-Catalyzed Living Radical Polymerizations. *ACS Macro Lett.* **2013**, *2* (1), 72-76
30. Yilmaz, G.; Yagci, Y.; Mechanistic Transformations Involving Radical and Cationic Polymerizations. *Chinese J. Polym. Sci.* **2020**, *38*, 205-212.
31. Kottisch, V.; Michaudel, Q.; Fors, B. P., Photocontrolled Interconversion of Cationic and Radical Polymerizations. *J. Am. Chem. Soc.* **2017**, *139* (31), 10665-10668.
32. Guerre, M.; Uchiyama, M.; Folgado, E.; Semsarilar, M.; Améduri, B.; Satoh, K.; Kamigaito, M.; Ladmiral, V., Combination of Cationic and Radical RAFT Polymerizations: A Versatile Route to Well-Defined Poly(ethyl vinyl ether)-block-poly(vinylidene fluoride) Block Copolymers. *ACS Macro Lett.* **2017**, *6* (4), 393-398.
33. Cianga, I.; Senyo, T.; Ito, K.; Yagci, Y., Electron Transfer Reactions of Radical Anions with TEMPO: A Versatile Route for Transformation of Living Anionic Polymerization into Stable Radical-Mediated Polymerization. *Macromol. Rapid Commun.* **2004**, *25* (19), 1697-1702.
34. Uchiyama, M.; Satoh, K.; McKenzie, T. G.; Fu, Q.; Qiao, G. G.; Kamigaito, M., Diverse approaches to star polymers via cationic and radical RAFT cross-linking reactions using mechanistic transformation. *Polym. Chem.* **2017**, *8* (38), 5972-5981.
35. Le, D.; Phan, T. N.; Autissier, L.; Charles, L.; Gimes, D., A well-defined block copolymer synthesis via living cationic polymerization and nitroxide-mediated polymerization using carboxylic acid-based alkoxyamines as a dual initiator. *Polym. Chem.* **2016**, *7* (8), 1659-1667.
36. Ciftci, M.; Kork, S.; Xu, G.; Buchmeiser, M. R.; Yagci, Y., Polyethylene-g-poly(cyclohexene oxide) by Mechanistic Transformation from ROMP to Visible Light-Induced Free Radical Promoted Cationic Polymerization. *Macromolecules* **2015**, *48* (6), 1658-1663.
37. Vaish, A.; Tsarevsky, V. N.; Hypervalent iodine-based dynamic and self-healing network polymers. *Polym. Chem.* **2019**, *10* (29), 3943-3950
38. Kumagai, S.; Nagai, K.; Satoh, K.; Kamigaito, M.; In-Situ Direct Mechanistic Transformation from RAFT to Living Cationic Polymerization for (Meth)acrylate-Vinyl Ether Block Copolymers. *Macromolecules* **2010**, *43* (18), 7523-7531.
39. Aoshima, H., Uchiyama, M., Satoh, K., Kamigaito, M., Interconvertible Living Radical and Cationic Polymerization through Reversible Activation of Dormant Species with Dual Activity. *Angew. Chem. Int. Ed.* **2014**, *53* (41), 10932-10936.
40. Matyjaszewski, K.; Xia, J.; Atom Transfer Radical Polymerization. *Chem. Rev.* **2001**, *101* (9), 2921-2990.
41. Matyjaszewski, K.; Tsarevsky, V. N.; Macromolecular Engineering by Atom Transfer Radical Polymerization. *J. Am. Chem. Soc.* **2014**, *136* (18), 6513-6533.
42. Chiefari, J.; Chong, Y. K.; Ercole, F.; Krstina, J.; Jeffery, J.; Le, T. P. T.; Mayadunne, R. T. A.; Meijs, G. F.; Moad, C. L.; Moad, G.; Rizzardo, E.; Thang, S. H., Living Free-Radical Polymerization by Reversible Addition-Fragmentation Chain Transfer: The RAFT Process. *Macromolecules* **1998**, *31* (16), 5559-5562.
43. Nothling, M. D.; Fu, Q.; Reyhani, A.; Allison-Logan, S.; Jung, K.; Zhu, J.; Kamigaito, M.; Boyer, C.; Qiao, G. G., Progress and Perspectives Beyond Traditional RAFT Polymerization. *Adv.Sci.* **2020**, *7* (20), 2001656.
44. Hawker, C. J.; Bosman, A. W.; Harth, E., New Polymer Synthesis by Nitroxide Mediated Living Radical Polymerizations. *Chem. Rev* **2001**, *101* (12), 3661-3688.
45. Goto, A.; Ohtsuki, A.; Ohfujii, H.; Tanishima, M.; Kaji, H., Reversible Generation of a Carbon-Centered Radical from Alkyl Iodide Using Organic Salts and Their Application as Organic Catalysts in Living Radical Polymerization, *J. Am. Chem. Soc.* **2013**, *135*(30) 11131-11139.
46. Ohtsuki, A.; Goto, A.; Kaji, H., Visible-Light-Induced Reversible Complexation Mediated Living Radical Polymerization of Methacrylates with Organic Catalysts. *Macromolecules* **2013**, *46* (1), 96-102.
47. Goto, A.; Suzuki, T.; Ohfujii, H.; Tanishima, M.; Fukuda, T.; Tsujii, Y.; Kaji, H., Reversible Complexation Mediated Living Radical Polymerization (RCMP) Using Organic Catalysts. *Macromolecules* **2011**, *44* (22), 8709-8715.
48. Wang, C. -G.; Chong, A. M. L.; Pan, H. M.; Sarkar, J.; Tay, X. T.; Goto, A., Recent Development in Halogen-Bonding-Catalyzed Living Radical Polymerization. *Polym. Chem.* **2020**, *11* (35), 5559-5571.
49. David, G.; Boyer, C.; Tonnar, J. Ameduri, B., Lacroix-Desmazes, P.; Boutevin, B., Use of Iodocompounds in Radical Polymerization. *Chem. Rev.* **2006**, *106* (9), 3936-3962
50. Wang, J.; Han, J.; Peng, H.; Tang, X.; Zhu, J.; Liao R. -Z.; Xie, X.; Xue Z.; Fliedel, C.; Poli R., Bromoalkyl ATRP initiator activation by inorganic salts: experiments and computations. *Polym. Chem.* **2019**, *10* (19), 2376-2386.
51. Miyamoto, M., Sawamoto, M., Higashimura, T., Living polymerization of isobutyl vinyl ether with hydrogen iodide/iodine initiating system. *Macromolecules* **1984**, *17* (3) 265 - 26
52. Faust, R., Kennedy, J. P., Living Carbocationic Polymerization. *Polym. Bull.* **1986**, *15*, 317-32
53. Kamigaito, M.; Sawamoto, M.; Higashimura, T., Living cationic polymerization of isobutyl vinyl ether by RCOOH/Lewis acid initiating systems: effects of carboxylate ions and Lewis acid activators. *Macromolecules* **1991**, *24* (14), 3988-3992.

54. Kahveci, M. U.; Oytun, F.; Yagci, Y., Influence of type of zinc salts on photoinitiated living cationic polymerization of vinyl ethers. *Polymer* **2013**, *54* (18), 4798-4801.

55. Ciftci, M.; Yoshikawa, Y.; Yagci, Y., Living Cationic Polymerization of Vinyl Ethers through a Photoinduced Radical Oxidation/Addition/Deactivation Sequence. *Angew. Chem. Int. Ed.* **2017**, *56* (2), 519-523.

56. Ciftci, M.; Yagci, Y., Block Copolymers by Mechanistic Transformation from PROAD to Iniferter Process. *Macromol. Rapid Commun.* **2018**, *39* (18), 1800464.

57. Aydogan, C.; Ciftci, M.; Yagci, Y., Controlled Synthesis of Block Copolymers by Mechanistic Transformation from Atom Transfer Radical Polymerization to Iniferter Process. *Macromol. Rapid Commun.* **2019**, *40* (14), 1900109.

Table of Contents

