

Self-cleaning glass with superhydrophobic coating

Wu, Yuanyuan

2013

Wu, Y. (2013, March). Self-cleaning glass with superhydrophobic coating. Presented at Discover URECA @ NTU poster exhibition and competition, Nanyang Technological University, Singapore.

<https://hdl.handle.net/10356/95899>

© 2013 The Author(s).

Downloaded on 28 Apr 2025 14:12:33 SGT

Category: 2
School of Materials Science and Engineering

Student: Wu Yuanyuan

Project ID: MSE12056

Climbing **so high**
to clean glass is
always my **head-**
ache!



Self-cleaning glass with superhydrophobic coating

Our interest

Skylights, sloped glazing, windows on high building: these are hard to access areas for cleaning. Our goal is to develop self cleaning glass!


Methodology

Make glass coating superhydrophobic by grafting hydrophobic groups on the surface.
(Superhydrophobic surfaces are extremely difficult to wet, with contact angle larger than 150° . This is also known as lotus effect.)



1. Experiment

- Modification of SiO_2 nanoparticles with HDMS
- Mixing different ratios of modified SiO_2 nanoparticles to MTMS coatings.

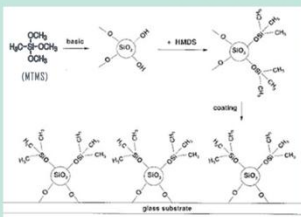

2. 2 Effect of curing temperature

After trying 100°C , 200°C and 300°C , it was found 200°C gives best result as at 100°C reaction is not thorough, but at 300°C , the hydrophobic groups ($-\text{CH}_3$) is destroyed.

Coated glass: water drop carries the dust and rolls away spontaneously.

Normal glass: water drop sticks on the glass with the dust.


2.3 Mechanical properties of the coating

- Hardness test
3 samples with silica ratio of 1:2:3 show pencil hardness of 5H, 6H, 6H respectively.


- Adhesion test
The more silica, the more adhesive the coating is on the glass.

2. Results and analysis

2.1 Surface morphology

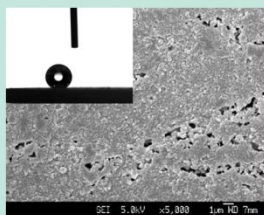

SEM image of superhydrophobic coating we developed. Inserted image is the corresponding water droplet image with contact angle 151° . (Water drop size: $4\mu\text{L}$)



1 SiO_2 , 2% coating stripped 2 SiO_2 , 5% coating stripped 3 SiO_2 , 40% coating stripped

3. Conclusion & vision

Superhydrophobic coating can be achieved by certain reactants choice, ratio, temperature etc. However, hardness and adhesion are also important for commercializing the coating. We have approached the matching of experimental results and our goal now. Future research will focus on how to achieve large hardness and adhesivity while maintaining large contact angle!